

On the Existence of Eshelby's Equivalent Ellipsoidal Inclusion Solution

William P. Kuykendall, William D. Cash, David M. Barnett, Wei Cai
Department of Mechanical Engineering, Stanford University, Stanford, CA 94305

November 28, 2011

Abstract

The existence of Eshelby's equivalent inclusion solution is proved for a degenerate "transformed" ellipsoidal inhomogeneity in an infinite anisotropic linear elastic matrix. We prove the invertibility of the fourth rank tensor expression, $\mathbf{C}'\mathcal{S}^E + \mathbf{C}(\mathbf{I} - \mathcal{S}^E)$, where \mathbf{C} is the stiffness tensor of the matrix, \mathbf{C}' is the stiffness tensor of the inhomogeneity, \mathcal{S}^E is the Eshelby tensor, and \mathbf{I} is the symmetric identity tensor. Taking advantage of the positive definiteness of certain tensor expressions, a proof-by-contradiction using energy arguments is posited that eliminates the possibility that the above expression is singular. Because the tensor expression is nonsingular, it can always be inverted and Eshelby's equivalent ellipsoidal inclusion method can be used to find the stress and strain fields in both the matrix and inhomogeneity.

1 Introduction

The problem of finding the stress fields resulting from an inhomogeneity has been investigated over the decades[1][2][3][4]. More than 50 years ago, Eshelby formulated a strategy for finding the stress field of a "transformed" ellipsoidal inhomogeneity in an infinite matrix[5]. He used the concept of an "equivalent inclusion," a method for replacing an inhomogeneity with elastic constants (C'_{ijkl}) different from those of the matrix with an inclusion. This inclusion has the same elastic constants (C_{ijkl}) as the matrix (Figure 1), but with an eigenstrain (denoted with e_{ij}^*), which is unknown and different from the actual transformation strain ($e_{ij}^{*'}$) prescribed for the transformed

inhomogeneity. For Eshelby’s equivalent inclusion method to work, the fictitious eigenstrain e_{ij}^* must be determined from

$$[(C'_{ijkl} - C_{ijkl})\mathcal{S}_{klmn}^E + C_{ijmn}]e_{mn}^* = C'_{ijkl}e_{kl}^*, \quad (1)$$

where e^{*} is the transformation strain actually prescribed for the inhomogeneity and \mathcal{S}^E is the Eshelby tensor. \mathcal{S}^E relates the eigenstrain e^* to the constrained strain e^c (i.e. the actual strain of the inclusion when embedded in the matrix), associated with the equivalent transformed inclusion, through the following equation:

$$e_{ij}^c = \mathcal{S}_{ijkl}^E e_{kl}^*. \quad (2)$$

If one uses a similar scheme employed in the “reduced” Voigt notation for linear elastic stiffnesses, Eq. (1) may be written as

$$[(C'_{IK} - C_{IK})\mathcal{S}_{KM}^E + C_{IM}]e_M^* = C'_{IM}e_M^*, \quad (3)$$

where all upper case indices range from 1 to 6. For more information on the Voigt notation, please refer to Appendix A. Solutions of Eq. (3) require that the 6×6 matrix $[(C' - C)\mathcal{S}^E + C]$ be non-singular. Eshelby did not discuss whether this matrix would always be nonsingular (and the problem would thus be solvable), or whether there exists some set of conditions that preclude obtaining such a solution. On physical grounds, one would expect Eshelby’s equivalent transformed inclusion method to always work, but for completeness a proof is desirable. Here we show that $[(C'_{IK} - C_{IK})\mathcal{S}_{KM}^E + C_{IM}]$ is always invertible so that the equivalent eigenstrain e_{ij}^* can always be found. The proof takes advantage of the positive definiteness of certain tensors appearing in energy arguments.

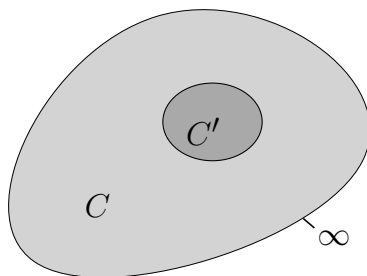


Figure 1: Inclusion inside an infinite matrix with different elastic constants.

To simplify the notation, we shall define a 6×6 matrix

$$A_{IM} \equiv (C'_{IK} - C_{IK})\mathcal{S}_{KM}^E + C_{IM}. \quad (4)$$

We can also write this equation in matrix form

$$\mathbf{A} = \mathbf{C}'\mathcal{S}^E + \mathbf{C}(\mathbf{I} - \mathcal{S}^E), \quad (5)$$

where \mathbf{I} is the symmetric identity matrix and \mathcal{S}^E is not symmetric. Note that all matrices here are real valued.

A real symmetric matrix \mathbf{B} is positive definite (P.D.) if[6]

$$\mathbf{x}^T \mathbf{B} \mathbf{x} \geq 0 \quad \forall \mathbf{x} \text{ real} \quad (6)$$

$$\mathbf{x}^T \mathbf{B} \mathbf{x} = 0 \quad \text{iff } \mathbf{x} = \mathbf{0}. \quad (7)$$

A **nonsymmetric** matrix \mathbf{A} is also P.D. if its symmetric portion ($\mathbf{B} = \frac{\mathbf{A} + \mathbf{A}^T}{2}$) is P.D.[7] (see Appendix B). A P.D. matrix has all positive eigenvalues (i.e. no zero or negative eigenvalues)[8]. Because the matrix does not have a zero eigenvalue, it is invertible and its determinant is nonzero. We will show that A is always invertible by utilizing the properties of P.D. matrices and the fact that the energy of an infinite elastic medium containing a finite-sized inclusion is inherently non-negative and bounded.

The paper is organized as follows. First, we will briefly review Eshelby's method in Section 2. Section 3 presents our proof that \mathbf{A} is always invertible. This is accomplished by first proving that both $\mathbf{C}(\mathbf{I} - \mathcal{S}^E)$ and $\mathbf{C}\mathcal{S}^E$ are P.D. and then using energy arguments to show that \mathbf{A} is nonsingular.

2 Eshelby's Method

2.1 Eshelby's Inclusion Problem

Eshelby showed[9] that the strain energy associated with a transformed ellipsoidal inclusion with a uniform eigenstrain e_I^* in an infinite matrix is

$$E = -\frac{1}{2}\sigma_I e_I^* V_0, \quad (8)$$

where σ_I is the stress in the transformed inclusion and V_0 is the volume of the inclusion. In the following, we give a brief review of Eshelby's method leading to Eq. (8), because the derivation will be useful for our proof.

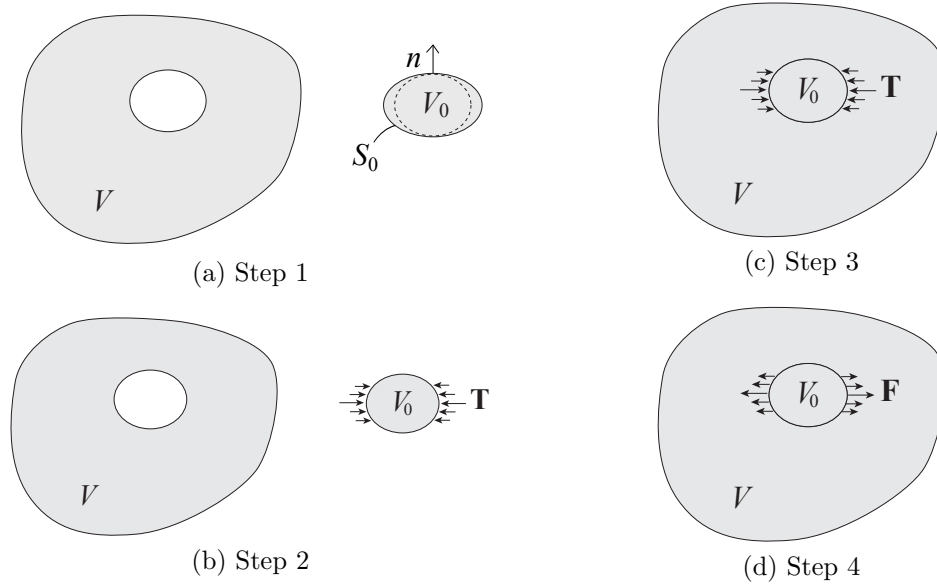


Figure 2: Steps to Solve Eshelby's Inclusion Problem.

Initially both matrix and the ellipsoidal inclusion are undeformed. The inclusion and matrix are separated (Figure 2a) and the inclusion alone is given the uniform stress-free transformation strain e_I^* . As e_I^* is inelastic strain and stress-free, there is no strain energy change in either the inclusion or the matrix. Tractions $-\sigma_{ij}^* n_i$ (where $\sigma_{ij}^* = C_{ijkl} e_{kl}^*$ and n_i is the outward facing unit normal of the inclusion) are applied to the inclusion boundary to “elastically” back-strain it to its original shape and size (Figure 2b), while the matrix remains undeformed. The strain energy change at the end of Step 1 is

$$\Delta W_1 = \frac{1}{2} \int_{V_0} \sigma_I^* e_I^* dV = \frac{1}{2} \sigma_I^* e_I^* V_0, \quad (9)$$

where V_0 is the volume of the inhomogeneity.

The inclusion is inserted back into the ellipsoidal “hole” in the matrix (Figure 2c), and the discontinuity in traction across the matrix-inhomogeneity interface is equivalent to a “body force”

$$f_j = \sigma_{ij}^* n_i dS \quad (10)$$

distributed over S_0 , the interface, where dS is a differential surface element of the interface. Relaxing this body force to zero (or equivalently adding on a solution to

remove this body force layer everywhere on S_0 , Figure 2d), produces an additional strain energy change

$$\Delta W_2 = -\frac{1}{2} \int_{S_0} \sigma_{ij}^* n_i u_j^c dS = -\frac{1}{2} \int_{V_0} \sigma_{ij}^* e_{ij}^c dV_0 = -\frac{1}{2} \sigma_I^* e_I^c V_0 = -\frac{1}{2} \sigma_I^c e_I^* V_0 \quad (11)$$

which is simply the average work done on S_0 in relaxing the layer of body force to zero. $e_I^c = \mathcal{S}_{IK}^E e_K^*$ is the “constrained” elastic strain (in Eshelby’s terminology) associated with e^* , and is thus uniform in V_0 . \mathcal{S}^E is the Eshelby tensor for the inclusion.

In its final state the transformed inclusion has undergone an elastic strain given by $e_I^c - e_I^*$ and its stress state is given by $\sigma_K^I = C_{KJ}(e_J^c - e_J^*)$, where the superscript “I” stands for inclusion. The total strain energy change in the system of inclusion and surrounding matrix is the sum of Eq. (9) and Eq. (11), namely

$$\Delta W = -\frac{1}{2} \sigma_K^I e_K^* V_0. \quad (12)$$

2.2 Eshelby’s Transformed Inhomogeneity Problem

Eshelby’s most clever method of solving the “transformed” inhomogeneity problem was to note that an ellipsoidal inhomogeneity (elastic stiffnesses \mathbf{C}' and eigenstrain $e^{*'}\prime$) can be replaced by an “equivalent” inclusion with elastic stiffness \mathbf{C} and eigenstrain e^* . We can apply Eshelby’s procedure in §2.1 to find the total strain and elastic strain inside the inhomogeneity and the equivalent inclusion:

$$e_I^{total} = e_I^c \quad (13)$$

$$e_I^{elastic} = e_I^c - e_I^* \quad (\text{for the inclusion}) \quad (14)$$

$$e_I^{elastic} = e_I^c - e_I^{*'} \quad (\text{for the inhomogeneity}). \quad (15)$$

As the total strains are the same, the inclusion may be replaced by the inhomogeneity with displacement continuity maintained at the inhomogeneity/matrix interface. Traction continuity is maintained with this switch if the stress in both inclusion and inhomogeneity are equal, i.e. if

$$C'_{IK}(e_K^c - e_K^{*'}) = C_{IK}(e_K^c - e_K^*). \quad (16)$$

This is the equation from which Eshelby’s equivalent inclusion method stems and is equivalent to Eq. (1) and Eq. (3). Eshelby assumed that an equivalent inclusion (e^*) can always be found for each transformed inhomogeneity ($e_I^{*'}, C'_{IK}$). This requires $\mathbf{A} = \mathbf{C}' \mathcal{S}^E + \mathbf{C}(\mathbf{I} - \mathcal{S}^E)$ to be invertible, which is the property we aim to prove in this paper.

3 Proof

3.1 Proving $\mathbf{C}(\mathbf{I} - \mathcal{S}^E)$ is P.D.

Energy arguments will be used to investigate the possible positive definite nature of $\mathbf{C}(\mathbf{I} - \mathcal{S}^E)$. Using Eq. (12) the inclusion energy can be written as

$$\begin{aligned}
 E &= \frac{1}{2} \sigma_I^* (e_I^* - \mathcal{S}_{IK}^E e_K^*) V_0 \\
 &= \frac{1}{2} \sigma_I^* (I_{IK} - \mathcal{S}_{IK}^E) e_K^* V_0 \\
 &= \frac{1}{2} C_{IM} e_M^* (I_{IK} - \mathcal{S}_{IK}^E) e_K^* V_0 \\
 &= \left[\frac{1}{2} e_M^* e_K^* V_0 \right] [C_{IM} (I_{IK} - \mathcal{S}_{IK}^E)].
 \end{aligned} \tag{17}$$

Because the left hand side of Eq. (17) is a strain energy (an inherently non-negative quantity for stable media), the right hand side must also be positive for any real eigenstrain e_I^* . Therefore, the matrix $\mathbf{C}(\mathbf{I} - \mathcal{S}^E)$ is P.D.

3.2 Proving $\mathbf{C}\mathcal{S}^E$ is P.D.

It is possible to show that $\mathbf{C}\mathcal{S}^E$ is also P.D. The energy change ΔW_2 in Eshelby's last step (see Figure 2d), must be negative, because we remove a constraint on the system (the layer of distributed body force) which then relaxes spontaneously to its final state.

$$\Delta W_2 = -\frac{1}{2} \sigma_I^* e_I^c V_0 = -\frac{1}{2} C_{IK} e_K^* \mathcal{S}_{IM}^E e_M^* V_0 \leq 0 \tag{18}$$

This leads to

$$e_K^* C_{KI} \mathcal{S}_{IM}^E e_M^* > 0, \tag{19}$$

meaning that $\mathbf{C}\mathcal{S}^E$ is P.D. According to Appendix B, $\det[\mathbf{C}\mathcal{S}^E] > 0$, even though $\mathbf{C}\mathcal{S}^E$ is not a symmetric matrix [8].

In the special case that $\mathbf{C}' = \lambda \mathbf{C}$, with $\lambda > 0$, we have:

$$\mathbf{A} = \lambda \mathbf{C}\mathcal{S}^E + \mathbf{C}(\mathbf{I} - \mathcal{S}^E), \tag{20}$$

so that \mathbf{A} is the sum of two P.D. matrices and must be P.D. This is a sufficient condition for \mathbf{A} being nonsingular. In general $\mathbf{C}'\mathcal{S}^E$ is not P.D. and \mathbf{A} is not P.D. However, we can still show that \mathbf{A} is always nonsingular (i.e. invertible).

3.3 Proving \mathbf{A} Is Invertible

The method of proof by contradiction will be used to show that \mathbf{A} is invertible. Suppose \mathbf{A} is singular (i.e. its determinant = 0), and \mathbf{A}^{-1} does not exist. Without the inverse, the equivalent inclusion strain, e_M^* cannot be found for a given C'_{IK} . Now consider C'_{IK} altered through a perturbation, i.e.:

$$C'_{IK} \longrightarrow C'_{IK} + \epsilon C_{IK}, \text{ where } \epsilon \geq 0. \quad (21)$$

Substituting this into Eq. (4) leads to a perturbed \mathbf{A} matrix as a function of ϵ .

$$\mathbf{A}(\epsilon) \equiv \mathbf{C}' \mathcal{S}^E + \epsilon \mathbf{C} \mathcal{S}^E + \mathbf{C}(\mathbf{I} - \mathcal{S}^E). \quad (22)$$

Note by assumption

$$\det[\mathbf{A}(\epsilon)] = 0 \quad \text{when } \epsilon = 0 \quad (23)$$

For sufficiently large values of ϵ , \mathbf{A} is dominated by the $\epsilon \mathbf{C} \mathcal{S}^E$ term, and

$$\det[\mathbf{A}(\epsilon)] \longrightarrow \epsilon^6 \det[\mathbf{C} \mathcal{S}^E] > 0. \quad (24)$$

This means that $\det[\mathbf{A}(\epsilon)]$ must be positive for sufficiently large ϵ . In addition, note that $\det[\mathbf{A}(\epsilon)]$ is a smooth (polynomial) function of ϵ . Hence, $\det[\mathbf{A}(\epsilon)]$ must also deviate from zero for arbitrarily small $\epsilon > 0$. For any infinitesimal ϵ , there exists a unique equivalent inclusion eigenstrain by solving Eq. (22).

$$\begin{aligned} A_{IK}(\epsilon) e_K^*(\epsilon) &= C'_{IK} e_K^{*'} \\ e^*(\epsilon) &= \mathbf{A}^{-1}(\epsilon) \mathbf{C}' e^{*'} \quad (\epsilon \rightarrow 0^+) \end{aligned} \quad (25)$$

Note that \mathbf{C}' is always invertible, meaning that $\mathbf{C}' e^{*'}$ spans the full 6-dimensional space. Because $\det[\mathbf{A}(\epsilon = 0)] = 0$, then $\det[\mathbf{A}^{-1}(\epsilon = 0)] \longrightarrow \infty$. Applying this to the right hand side of Eq. (25) as $\epsilon \rightarrow 0^+$ yields

$$\lim_{\epsilon \rightarrow 0^+} \mathbf{A}^{-1}(\epsilon) \mathbf{C}' e^{*' \prime} \longrightarrow \infty. \quad (26)$$

This would mean:

$$\lim_{\epsilon \rightarrow 0^+} e^*(\epsilon) \longrightarrow \infty. \quad (27)$$

This implies that the equivalent inclusion eigenstrain is unbounded for \mathbf{A} close to singular. We assume the problem at hand is not the trivial case of a singularity caused by $a \rightarrow 0$, $b \rightarrow 0$, or $c \rightarrow 0$ (a, b, c are the major/minor axes of the ellipsoid)

and that \mathbf{C} and \mathbf{C}' are always invertible. Then $\lim_{\epsilon \rightarrow 0^+} e^*(\epsilon) \rightarrow \infty$ would imply that the total strain of the equivalent inclusion e^I , which is the same as the total strain of the inhomogeneity $e^{I'}$, will go to infinity as $\epsilon \rightarrow 0$. This would mean the elastic energy stored in the matrix will become unbounded as $\epsilon \rightarrow 0$, which is physically impossible because the energy in the matrix must be smaller than the energy stored in the inhomogeneity when it is subjected to an elastic strain that exactly cancels the transformed strain (i.e. when $e^{I',tot} = e^{I',elastic} + e^{*'} = 0$). This means $E < \frac{1}{2} \sigma_I^{*'} e_I^{*'} V_0$.

Because $e^*(\epsilon)$ cannot get arbitrarily large from infinitesimal changes of \mathbf{C}' , the possibility that $\lim_{\epsilon \rightarrow 0} \det[\mathbf{A}(\epsilon)] = 0$ must be discarded, a contradiction to the initial assumption. Thus \mathbf{A} must always be invertible.

4 Conclusions

We used the P.D. nature of two tensors combined with energy arguments used by Eshelby in his original approach to show that the matrix \mathbf{A} defined in Eq. (5) must be invertible. Since \mathbf{A} has this property (for nontrivial \mathbf{C} , i.e. matrix is not rigid or infinitely pliant), Eq. (1) can always be solved for e^* . The method outlined above only applies for the one scenario corresponding to Eq. (1) (initially strained inhomogeneity with different elastic constants than the surrounding infinite matrix, with no applied external fields), however a similar approach can be used to explore the solvability of other situations.

5 Acknowledgements

William Kuykendall and William D. Cash are supported by Stanford Graduate Fellowships. Wei Cai wishes to thank Professor W. Cai of the University of North Carolina, Charlotte for useful discussions regarding Appendix B.2. This work is partly supported by an NSF grant CMS-0547681.

References

- [1] Eshelby, JD. The elastic field outside an ellipsoidal inclusion. Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences, Vol. 252, No. 1271, pp. 561-569 (Oct. 1959).
- [2] Willis, JR. Anisotropic elastic inclusion problems. Quarterly Journal of Mechanics and Applied Mathematics, Vol. 17, Issue 2, pp. 157-174 (May 1964).

- [3] Walpole, L.J. The elastic field of an inclusion in an anisotropic medium. Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences, Vol. 300, No. 1461, pp. 270-289 (Aug. 1967).
- [4] Li, JY and Dunn, ML. Anisotropic coupled-field inclusion and inhomogeneity problems. Philosophical Magazine A, Vol. 77, No. 5, pp. 1341-1350 (1998).
- [5] Eshelby, JD. The determination of the elastic field of an ellipsoidal inclusion, and Related Problems. Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences, Vol. 241, No. 1226, pp. 376-396 (Aug. 1957).
- [6] Strang, G. Linear Algebra and its Applications, Fourth Edition, Chapter 6, Thomson Brooks/Cole, 2006.
- [7] Higham, NJ. Accuracy and Stability of Numerical Algorithms. Society for Industrial and Applied Mathematics, p. 223 (1996).
- [8] Harville, D.A. Matrix Algebra from a Statistician's Perspective, Chapter 14, Springer, 2008.
- [9] Weinberger, C.R. Cai, W. Barnett, D.M. ME340B Lecture Notes, Elasticity of Microscopic Structures, Chapter 2, 2005. http://micro.stanford.edu/~caiwei/me340b/content/me340b-notes_v01.pdf
- [10] Nye, JF. Physical Properties of Crystals: Their Representation by Tensors and Matrices, Chapter 8, Clarendon Press, Oxford (1985).

A Voigt Notation

Our proof used arguments based on properties (like P.D.) and operations (like determinants) traditionally associated with matrices. A symmetric fourth-rank tensor may be reduced to a symmetric matrix using the Voigt form. However, this reduction in order requires the use of weights to recover losses associated with the symmetries of the tensor. There are different approaches to the weights, but in this paper the Nye notation will be used[10]. In the fourth-rank tensors presented below the 81 components reduce to 36 distinct components represented in a 6×6 matrix

due to minor symmetries (i.e. $C_{ijkl} = C_{jikl}$ and $C_{ijkl} = C_{ijlk}$).

$$\begin{aligned}
& \begin{pmatrix} C_{11} & C_{12} & C_{13} & C_{14} & C_{15} & C_{16} \\ C_{21} & C_{22} & C_{23} & C_{24} & C_{25} & C_{26} \\ C_{31} & C_{32} & C_{33} & C_{34} & C_{35} & C_{36} \\ C_{41} & C_{42} & C_{43} & C_{44} & C_{45} & C_{46} \\ C_{51} & C_{52} & C_{53} & C_{54} & C_{55} & C_{56} \\ C_{61} & C_{62} & C_{63} & C_{64} & C_{65} & C_{66} \end{pmatrix} = \\
& \begin{pmatrix} C_{1111} & C_{1122} & C_{1133} & C_{1123} & C_{1113} & C_{1112} \\ C_{2211} & C_{2222} & C_{2233} & C_{2223} & C_{2213} & C_{2212} \\ C_{3311} & C_{3322} & C_{3333} & C_{3323} & C_{3313} & C_{3312} \\ C_{2311} & C_{2322} & C_{2333} & C_{2323} & C_{2313} & C_{2312} \\ C_{1311} & C_{1322} & C_{1333} & C_{1323} & C_{1313} & C_{1312} \\ C_{1211} & C_{1222} & C_{1233} & C_{1223} & C_{1213} & C_{1212} \end{pmatrix} \\
& \begin{pmatrix} \mathcal{S}_{11}^E & \mathcal{S}_{12}^E & \mathcal{S}_{13}^E & \mathcal{S}_{14}^E & \mathcal{S}_{15}^E & \mathcal{S}_{16}^E \\ \mathcal{S}_{21}^E & \mathcal{S}_{22}^E & \mathcal{S}_{23}^E & \mathcal{S}_{24}^E & \mathcal{S}_{25}^E & \mathcal{S}_{26}^E \\ \mathcal{S}_{31}^E & \mathcal{S}_{32}^E & \mathcal{S}_{33}^E & \mathcal{S}_{34}^E & \mathcal{S}_{35}^E & \mathcal{S}_{36}^E \\ \mathcal{S}_{41}^E & \mathcal{S}_{42}^E & \mathcal{S}_{43}^E & \mathcal{S}_{44}^E & \mathcal{S}_{45}^E & \mathcal{S}_{46}^E \\ \mathcal{S}_{51}^E & \mathcal{S}_{52}^E & \mathcal{S}_{53}^E & \mathcal{S}_{54}^E & \mathcal{S}_{55}^E & \mathcal{S}_{56}^E \\ \mathcal{S}_{61}^E & \mathcal{S}_{62}^E & \mathcal{S}_{63}^E & \mathcal{S}_{64}^E & \mathcal{S}_{65}^E & \mathcal{S}_{66}^E \end{pmatrix} = \\
& \begin{pmatrix} \mathcal{S}_{1111}^E & \mathcal{S}_{1122}^E & \mathcal{S}_{1133}^E & \mathcal{S}_{1123}^E & \mathcal{S}_{1113}^E & \mathcal{S}_{1112}^E \\ \mathcal{S}_{2211}^E & \mathcal{S}_{2222}^E & \mathcal{S}_{2233}^E & \mathcal{S}_{2223}^E & \mathcal{S}_{2213}^E & \mathcal{S}_{2212}^E \\ \mathcal{S}_{3311}^E & \mathcal{S}_{3322}^E & \mathcal{S}_{3333}^E & \mathcal{S}_{3323}^E & \mathcal{S}_{3313}^E & \mathcal{S}_{3312}^E \\ 2\mathcal{S}_{2311}^E & 2\mathcal{S}_{2322}^E & 2\mathcal{S}_{2333}^E & 2\mathcal{S}_{2323}^E & 2\mathcal{S}_{2313}^E & 2\mathcal{S}_{2312}^E \\ 2\mathcal{S}_{1311}^E & 2\mathcal{S}_{1322}^E & 2\mathcal{S}_{1333}^E & 2\mathcal{S}_{1323}^E & 2\mathcal{S}_{1313}^E & 2\mathcal{S}_{1312}^E \\ 2\mathcal{S}_{1211}^E & 2\mathcal{S}_{1222}^E & 2\mathcal{S}_{1233}^E & 2\mathcal{S}_{1223}^E & 2\mathcal{S}_{1213}^E & 2\mathcal{S}_{1212}^E \end{pmatrix}
\end{aligned}$$

Note that in the Nye notation, the matrix notation of Eshelby's tensor is different from that of the elastic stiffness tensor \mathbf{C} . This is because \mathbf{C} describes the relation between stress and strain, while \mathcal{S}^E describes the relation between two strain tensors. The second rank tensors can also be reduced to a vector formulation.

$$\begin{pmatrix} e_1 \\ e_2 \\ e_3 \\ e_4 \\ e_5 \\ e_6 \end{pmatrix} = \begin{pmatrix} e_{11} \\ e_{22} \\ e_{33} \\ 2e_{23} \\ 2e_{13} \\ 2e_{12} \end{pmatrix} \quad \begin{pmatrix} \sigma_1 \\ \sigma_2 \\ \sigma_3 \\ \sigma_4 \\ \sigma_5 \\ \sigma_6 \end{pmatrix} = \begin{pmatrix} \sigma_{11} \\ \sigma_{22} \\ \sigma_{33} \\ \sigma_{23} \\ \sigma_{13} \\ \sigma_{12} \end{pmatrix}$$

B Positive Definite Non-Symmetric Matrices

B.1 Definition

The positive definiteness of non-symmetric matrices depends on the positive definiteness of the symmetric part of the non-symmetric matrix[7]. As mentioned earlier, a matrix (\mathbf{A}) can be separated into a symmetric (\mathbf{B}) and an antisymmetric (\mathbf{D}) part as:

$$\begin{aligned}\mathbf{A} &= \mathbf{B} + \mathbf{D} \\ \mathbf{B} &= \frac{\mathbf{A} + \mathbf{A}^T}{2} \\ \mathbf{D} &= \frac{\mathbf{A} - \mathbf{A}^T}{2}\end{aligned}$$

\mathbf{B} and \mathbf{D} can be substituted into the definition of P.D., yielding

$$\mathbf{x}^T \mathbf{A} \mathbf{x} = \mathbf{x}^T (\mathbf{B} + \mathbf{D}) \mathbf{x} = \mathbf{x}^T \mathbf{B} \mathbf{x} + \mathbf{x}^T \mathbf{D} \mathbf{x} = \mathbf{x}^T \mathbf{B} \mathbf{x} \quad (28)$$

because $\mathbf{x}^T \mathbf{D} \mathbf{x} = 0$. Thus if the symmetric term is positive definite, the entire non-symmetric matrix is positive definite.

The fact that all eigenvalues are positive comes immediately from this result. If \mathbf{x} is a right eigenvector of nonsymmetric P.D. matrix \mathbf{A} with eigenvalue λ , then

$$\begin{aligned}\mathbf{A} \mathbf{x} &= \lambda \mathbf{x} \\ \mathbf{x}^T \mathbf{A} \mathbf{x} &= \mathbf{x}^T \lambda \mathbf{x} \\ \lambda &= \frac{\mathbf{x}^T \mathbf{A} \mathbf{x}}{\mathbf{x}^T \mathbf{x}}\end{aligned}$$

where the numerator is positive due to \mathbf{A} being P.D. and the denominator is simply the norm of \mathbf{x} , a non-negative quantity. Thus, λ must be positive.

B.2 Determinant

In this appendix, we show that the determinant of a non-symmetric P.D. matrix is positive. We give the proof here for completeness, because most of the discussion on positive definiteness in the literature focuses on symmetric matrices, with the exception of [8]. Suppose \mathbf{H} is an $N \times N$, real, symmetric, P.D. matrix (i.e. $\mathbf{H} = \mathbf{H}^T$, $\mathbf{x}^+ \mathbf{H} \mathbf{x} > 0 \quad \forall \mathbf{x} \neq 0$, and $\det(\mathbf{H}) > 0$, where \mathbf{x}^+ indicates the complex transpose) and suppose \mathbf{D} is a real, antisymmetric matrix (i.e. $\mathbf{D}^T = -\mathbf{D}$). To show that the

determinant of a positive definite, real, non-symmetric matrix has to be positive, it is equivalent to show $\det(\mathbf{H} + \mathbf{D}) > 0$.

Since \mathbf{H} is real, symmetric, and P.D., \mathbf{H}^{-1} is also real, symmetric, and P.D. This means that $-\mathbf{D}\mathbf{H}^{-1}\mathbf{D}$ is a real, symmetric, semi-definite matrix because

$$\begin{aligned} -\mathbf{x}^+\mathbf{D}\mathbf{H}^{-1}\mathbf{D}\mathbf{x} &= (\mathbf{D}\mathbf{x})^+\mathbf{H}^{-1}(\mathbf{D}\mathbf{x}) > 0 & \text{iff } \mathbf{D}\mathbf{x} \neq 0 \\ -\mathbf{x}^+\mathbf{D}\mathbf{H}^{-1}\mathbf{D}\mathbf{x} &= 0 & \text{iff } \mathbf{D}\mathbf{x} = 0. \end{aligned}$$

We can also state that $\mathbf{x}^T\mathbf{D}\mathbf{x}$ is purely imaginary or zero because

$$(\mathbf{x}^+\mathbf{D}\mathbf{x})^* = x_i D_{ij}^* x_j^* = x_i D_{ij} x_j^* = x_j^* D_{ij} x_i = x_j^* (-D_{ji}) x_i = -(\mathbf{x}^+\mathbf{D}\mathbf{x}). \quad (29)$$

This is an expansion of what was found in the first part of this appendix.

We can also state that $\mathbf{H}^{-1}\mathbf{D}$ has no real eigenvalues λ , with the possible exception of $\lambda = 0$. This can be shown by supposing $\mathbf{H}^{-1}\mathbf{D}\mathbf{x} = \lambda\mathbf{x}$, with $\lambda \neq 0$, which also indicates that $\mathbf{D}\mathbf{x} \neq 0$. Then

$$0 < -\mathbf{x}^+\mathbf{D}\mathbf{H}^{-1}\mathbf{D}\mathbf{x} = -\mathbf{x}^+\mathbf{D}(\lambda\mathbf{x}) = -\lambda\mathbf{x}^+\mathbf{D}\mathbf{x} \quad (30)$$

because $\mathbf{x}^+\mathbf{D}\mathbf{x}$ is purely imaginary (it is not zero in this case). Thus, λ must be purely imaginary to make $-\lambda\mathbf{x}^+\mathbf{D}\mathbf{x} > 0$.

Hence $\det(\lambda\mathbf{I} - \mathbf{H}^{-1}\mathbf{D}) = 0$ has no real roots, except possibly $\lambda = 0$. Equivalently, $\det(\lambda\mathbf{I} + \mathbf{H}^{-1}\mathbf{D}) = 0$ has no real roots, except possibly $\lambda = 0$. Excluding the possibility that $\lambda = 0$ yields

$$0 \neq \det(\lambda\mathbf{I} + \mathbf{H}^{-1}\mathbf{D}) \equiv f(\lambda). \quad (31)$$

In fact, we also know that

$$f(\lambda) > 0 \quad \lambda \rightarrow \infty \quad (32)$$

Since there are no real roots and $f(\lambda) > 0$ at some point, $f(\lambda) > 0 \quad \forall \lambda > 0$. From here, we can let $\lambda = 1$ to get $f(1) = \det(\mathbf{I} + \mathbf{H}^{-1}\mathbf{D}) > 0$. Thus

$$\det(\mathbf{H} + \mathbf{D}) = \det[\mathbf{H}(\mathbf{I} + \mathbf{H}^{-1}\mathbf{D})] = \det(\mathbf{H}) \cdot \det(\mathbf{I} + \mathbf{H}^{-1}\mathbf{D}) > 0, \quad (33)$$

since $\det(\mathbf{H}) > 0$ and $\det(\mathbf{I} + \mathbf{H}^{-1}\mathbf{D}) > 0$.